

Evidence for Oxygen Holes due to d - p Rehybridization in Thermoelectric $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$

Y. Ishida,¹ T. Baba,¹ R. Eguchi,¹ M. Matsunami,¹ M. Taguchi,¹ A. Chainani,¹

Y. Senba,² H. Ohashi,² Y. Okamoto,³ H. Takagi,⁴ and S. Shin^{1,3}

¹RIKEN SPring-8 Center, Sayo, Sayo, Hyogo 679-5148, Japan

²JASRI/SPring-8, Sayo, Sayo, Hyogo 679-5198, Japan

³ISSP, University of Tokyo, Kashiwa-no-ha, Kashiwa, Chiba 277-8561, Japan

⁴RIKEN, The Institute for Physical and Chemical Research, Wako, Saitama 351-0198, Japan

(Dated: July 31, 2009)

Soft-x-ray photoemission and absorption spectroscopies are employed to investigate the electronic structures of $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$. Similarly to the layered cobaltates such as $\text{Na}_{1-x}\text{CoO}_2$, a valence-band satellite feature (VBS) occurs at higher binding energy to the O $2p$ band. We find that the VBS resonates at the O $1s$ edge. Additionally, core absorption shows clear x dependence in the O $1s$ edge rather than in the Rh $3p$ edge. These results indicate that the holes in the initial state mainly have O $2p$ character presumably due to d - p rehybridizations affected by Sr^{2+} vacancy potentials. The resultant inhomogeneous charge texture may have impact on the TE transport properties at low x .

PACS numbers:

The search for efficient thermoelectric (TE) materials is extensively pursued with the aim at practical applications such as TE batteries and Peltier refrigerators [1]. Since metallic materials had been considered to exhibit poor TE performance [1], it was a surprise that a low-resistive layered cobaltate $\text{Na}_{1-x}\text{CoO}_2$ ($x < 0.5$) exhibited large TE power (Q) at high temperatures [2, 3]. The cobaltates have gained further interest as exhibiting rich phase diagram [4] including superconductivity [5] and 3D magnetism [6, 7]. The largeness of Q has been discussed from a band-theoretical viewpoint [8, 9, 10, 11] or from a correlated viewpoint [12, 13, 14, 15], or from a viewpoint that there is a coherent-to-incoherent crossover in the low-energy excitations with increasing T [16, 17]. Furthermore, interesting Na orderings [18, 19] that affect the electronic properties [20, 21, 22] have been reported, but their impact on the TE properties is not clear at present.

From a band-theoretical viewpoint, the valence band of NaCoO_2 consists of a filled t_{2g} band positioned just below the chemical potential (μ) and an O $2p$ band at higher binding energy (E_B) as schematically shown in the upper panel of Fig. 1(a). With Na^+ deintercalation, μ is shifted into the t_{2g} band, and holes of mainly t_{2g} character are introduced into the triangular lattice of Co^{3+} ions. Valence-band spectra of $\text{Na}_{0.7}\text{CoO}_2$ recorded by photoemission spectroscopy (PES) indeed show the t_{2g} and the O $2p$ bands, but in addition, there is a valence-band satellite feature (VBS) at $E_B \sim 11$ eV [23] as schematically shown in the lower panel of Fig. 1(a). Similar VBSs occur in other layered cobaltates such as LiCoO_2 [24] and $\text{Ca}_3\text{Co}_4\text{O}_9$ [9] (VBSs in TE Bi-Sr-Co-O system are obscured by Bi $6s$ states at $E_B \sim 11$ eV [25]). Thus, the VBS is a ubiquitous feature in the TE cobaltates, which is missing in the band-theoretical density of states (DOS).

Herein, we investigate element-specific electronic structures of $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ [26] using soft-x-ray absorption (XAS) and resonant PES. $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ is structurally and electronically analogous to $\text{Na}_{1-x}\text{CoO}_2$: hole carriers are introduced into the layered triangular lattice of

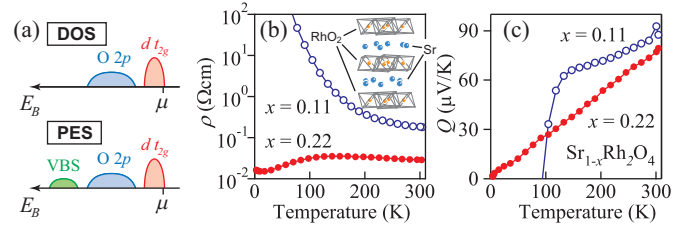


FIG. 1: $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$, an analogue of $\text{Na}_{1-x}\text{CoO}_2$. (a) Electronic structure. The band theoretical DOSs of the cobaltates and the rhodates exhibit t_{2g} and O $2p$ bands, but the valence-band PES spectra additionally exhibit VBSs. Resistivity (b) and TE power (c) of $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ as functions of temperature. The crystal structure of SrRh_2O_4 is shown in the inset of (b).

low-spin Rh ions (nominally t_{2g}^6) through Sr^{2+} deintercalation [inset of Fig. 1(b)] to show insulator-to-metal transition at $x \sim 0.2$ [Fig. 1(b)], and the $x = 0.22$ sample shows $Q \sim 70 \mu\text{V/K}$ at 300 K [Fig. 1(c)] [26]. Similarly to the cobaltates [9, 23, 24], we find a VBS in $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$. Moreover, the VBS resonates at the O $1s$ edge followed by O $1s2p2p$ Auger emissions, providing strong constraints on its origin. We also find clear x dependence in the O $1s$ XAS rather than in the Rh $3p$ XAS. The results indicate that holes in $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ have strong O $2p$ character presumably due to so-called d - p rehybridizations [27, 28, 29, 30] that redistribute the holes from d states to p states beyond a rigid-band-shift picture.

Single-phase well-sintered $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ ($x = 0.11$ and 0.22) were prepared by a conventional solid state reaction as described elsewhere [26]. The resistivity (ρ) and Q of the samples [Fig. 1(b) and (c), respectively] nicely reproduced those reported previously [26]. XAS and PES were performed at BL17SU of SPring-8 equipped with a VG Scienta SES2002 analyzer [31]. Sample surfaces were obtained by fracturing the samples inside the spec-

trometer under ultrahigh vacuum ($< 5 \times 10^{-8}$ Pa). XAS spectra were recorded at 300 K in the total electron yield method. PES spectra were recorded at 50 K at ~ 250 -meV energy resolution and E_B was referenced to μ of Au in contact with the sample and the analyzer. PES spectra were normalized to the incident photon flux.

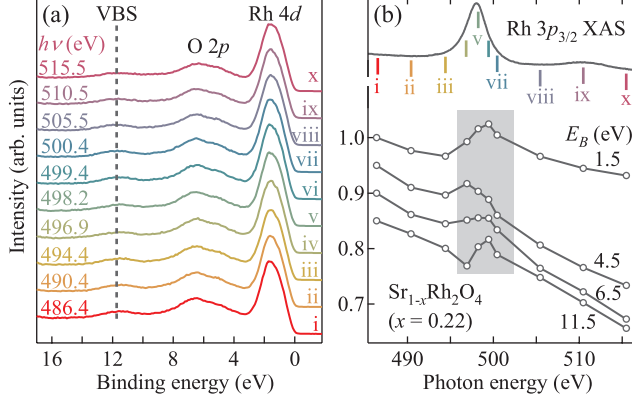


FIG. 2: Rh $3p$ - $4d$ resonant PES of $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ ($x=0.22$). (a) Valence-band spectra recorded across the Rh $3p_{3/2}$ edge. (b) CIS spectra and Rh $3p_{3/2}$ XAS. CIS spectra are normalized to the intensity at 486.4 eV and have arbitrary offsets. The labels (i-x) on the spectra in (b) correspond to the photon energies indicated by bars on the Rh $3p_{3/2}$ XAS in (c).

Figure 2(a) shows valence-band spectra of $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ ($x=0.22$) recorded across the Rh $3p_{3/2}$ edge. We find a VBS at $E_B \sim 11.7$ eV, a feature missing in the LDA DOS [32], as well as the Rh $4d$ and the O $2p$ bands centered at $E_B \sim 1.5$ and 6 eV, respectively. Figure 2(b) shows constant-initial-state (CIS) spectra at $E_B = 1.5, 4.5, 6.5$, and 11.5 eV. One can see resonant enhancement of Rh $4d$ states at the Rh $3p_{3/2}$ edge [shaded area in Fig. 2(b)] in all features including the VBS (CIS at $E_B = 11.5$ eV). This indicates that the Rh $4d$ weight is spread over a wide energy range and that the VBS has some Rh $4d$ character. The presence of the Co $3d$ character in the VBSs of the cobaltates was similarly confirmed through Co $3d$ resonant PES [9, 23, 24].

Next, we performed resonant PES at the O $1s$ edge to obtain information about the O $2p$ states. Figure 3(a) and (b) show, respectively, the valence-band spectra recorded in the vicinity of the O $1s$ edge and the difference to the off-resonant spectra recorded at $h\nu = 523.0$ eV. One can see that the VBS resonates at $h\nu = 527.5$ eV, and subsequently, O $1s2p2p$ Auger peak emerges from the vicinity of the VBS. The results indicate that the final state of the 11.7-eV VBS is similar to that of the O $1s2p2p$ Auger emission, namely, the O $2p$ -two-hole final state [see schematic in Fig. 3(a)]. This interpretation is the same as that of the 6-eV satellite of Ni identified to a Ni $3d$ -two-hole final state [33]. In order to reach the O $2p$ two-hole final state by photoemission, the initial state should contain an electronic configuration that has a single hole in the O $2p$ state. We here-

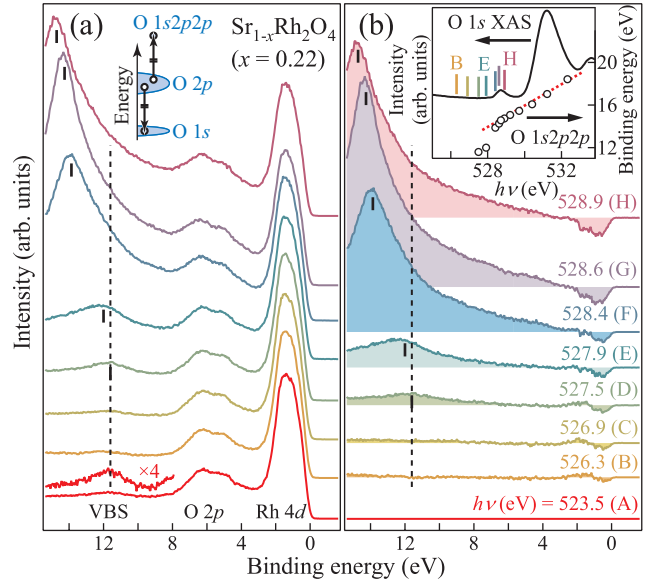


FIG. 3: Valence-band spectra of $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ ($x=0.22$) recorded across the O $1s$ edge. (a) Valence-band spectra recorded in the vicinity of the O $1s$ edge. Inset shows a schematic of the final state of an O $1s2p2p$ Auger-electron emission. (b) Difference spectra to the 523.0-eV spectrum. The labels (A-H) on the spectra correspond to the photon energies indicated on the O $1s$ XAS in the inset in (b). The dotted vertical lines indicate the 11.7-eV VBS, and the bars indicate the O $1s2p2p$ Auger peaks. The O $1s2p2p$ Auger peak positions are plotted in the inset in (b), in which the dotted line indicates the constant kinetic energy.

after denote the initial oxygen-hole configuration as p_v^5 . We note that the p_v^5 state is different from the ligand-hole states of the configuration-interaction CoO_6 cluster-model analyses [34, 35], since the p_v^5 state is considered to be affected by the cation vacancy potentials [36] (discussed later). At $h\nu \geq 528.7$ eV, the O $1s2p2p$ Auger peak position is shifted to higher E_B since the kinetic energy of an O $1s2p2p$ Auger electron is independent of $h\nu$ [inset in Fig. 3(c)]. The resonant peak position at $h\nu = 527.5$ eV slightly deviates from the constant kinetic energy of the normal O $1s2p2p$ Auger, perhaps since the p_v^5 configuration is mixed to some d -hole configurations as inferred from the Rh $4d$ resonant PES [Fig. 2].

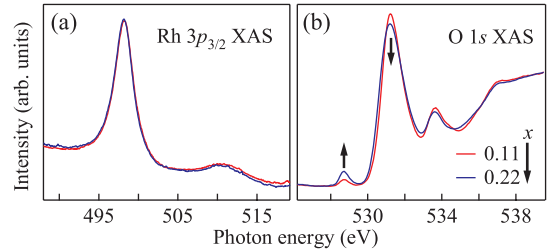


FIG. 4: Rh $3p_{3/2}$ (a) and O $1s$ (b) XAS. The arrows in (b) indicate the change with increasing x .

Evidence for oxygen holes in the initial state is also found in the XAS as shown in Fig. 4. With increasing x , the height of the prepeak feature in the O 1s XAS at $h\nu=528.7\text{eV}$ becomes large and that of the main peak at $h\nu=531.2\text{eV}$ becomes small (for each composition, the line shape at $h\nu<533\text{eV}$ was reproducible for 3 fractures). On the other hand, the Rh 3p XAS is hardly changed with x . Since the O 1s prepeak intensity is almost in proportional to x , we assign it to Sr-vacancy induced states mainly having O 2p character, so that the prepeak is assigned to $(1s)^2(2p_v^5) \rightarrow (1s)^1(2p^6)$. The spectral-weight transfer seen in O 1s XAS is often taken as a signature of strong electron correlation [34]. In the XAS studies of $(\text{Li}/\text{Na})_{1-x}\text{CoO}_2$ [37, 38, 39], main changes with x occurred in the O 1s XAS rather than in the Co 2p XAS. Thus, oxygen holes in the initial state are common features in the TE rhodates and cobaltates.

The oxygen holes in $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ revealed by resonant PES and XAS at the O 1s edge indicate that the electronic-structure evolution with x goes beyond a rigid-band-shift picture. Otherwise, μ would shift with increasing x into the Rh 4d band resulting in holes that mainly have Rh 4d character. The spectral weight should therefore be redistributed with increasing x , most likely due to d - p rehybridization [27, 28, 29, 30]: as evidenced from the charge densities calculated [40] for $\text{Li}_{1-x}\text{CoO}_2$ [27, 28] and $\text{Na}_{1-x}\text{CoO}_2$ [29], the holes introduced via Li/Na deintercalation are not homogeneously distributed in the Co layers but reside at oxygen sites neighboring the Li/Na vacancies, i.e., the cation vacancy potential binds the holes to form the p_v^5 state [28]. The charge density at a Co site was nearly unchanged with increasing x [27, 28, 29], since the t_{2g} holes were dressed by e_g electrons transferred from the O 2p states through the d - p rehybridization. The essence of the charge rearrangement with doping can be captured in a simple model, namely, transition-metal impurities in semiconductors [30, 41]. The rigidity of the Rh 3p XAS line shape with x [Fig. 4(a)] is thus considered as a fingerprint that the d - p rehybridization is self-regulating the local charge density about the Rh site to a nearly constant value.

A striking difference between the O 1s XAS of $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ and those of $(\text{Na}/\text{Li})_{1-x}\text{CoO}_2$ [34, 37, 38, 39] is that the x -dependent prepeak in the former is well separated from the main peak [Fig. 4(b)], whereas those in the latter are merging into the main peaks. This can be understood that the degree of localization of the p_v^5 state is affected by the strength of the cation vacancy potentials. Since the divalent Sr^{2+} vacancy potential is stronger than those of the monovalent Li^+/Na^+ , the holes are more strongly bound around the vacancies in the former than in the latter [28]. Hence, the p_v^5 state appears to be more localized in $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$, so that the prepeak appears to be a sharp level. The localized character of the p_v^5 state is supported by an ^{17}O NMR study of $\text{Na}_{1-x}\text{CoO}_2$ ($x=0.28$), revealing that $\sim 30\%$ of the oxygen sites carry local magnetic moments [42]. We naturally identify these magnetic oxygens to have the p_v^5

configuration.

It should be noted that a VBS was also observed in stoichiometric LiCoO_2 having no Li vacancies [24]. Through a configuration-interaction cluster-model analysis, the VBS of LiCoO_2 was attributed to large d - p hybridization and orbital degeneracy of the d states [24]. Thus, the d - p rehybridization with doping effectively occurs when the parent compound has large d - p hybridization and orbital degeneracy. Large d - p hybridization generally occurs in t_{2g} electron system having unoccupied e_g orbitals (this includes d^0 insulators [43, 44]). In fact, d - p rehybridization was reported to occur when carriers are doped into SrTiO_3 , a nominally d^0 insulator [45]. It is also interesting that a layered Cu_xTiSe_2 , which shows TE properties as good as the cobaltates [46], is also considered to exhibit d - p rehybridization [47]. Here, the hybridization of the Se 4p states into the unoccupied Ti 3d states opens the channel of d - p rehybridization, and Cu^+ act as a source of “occupancy” potential. Thus, the TE cobaltates, rhodates, and the intercalated Ti dichalcogenides can be categorized to those exhibiting d - p rehybridization affected by the cation vacancy/occupancy potentials.

Since the holes in the initial state are not homogeneously distributed in the Rh layers as expected in a rigid-band-shift picture but are further redistributed due to the d - p rehybridizations and the Sr vacancy potentials, the charge density is considered to be nonperiodic compared to the crystallographic periodicity of SrRh_2O_4 (please see the nonperiodic charge densities calculated for $(\text{Li}/\text{Na})_{1-x}\text{CoO}_2$ [27, 28, 29].) Thus, it would be necessary to realize that the transport is occurring on such an inhomogeneous charge texture with O 2p holes bound to cation vacancies. For example, as was pointed out in [32], the nonmetallic conduction at $x \lesssim 0.2$ of $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ [26] can be viewed as a variable-range hopping, i.e., the low-energy excitations relevant to the transport show weak localizations as they are subject to randomness [48]. The mobility-edge crossing occurring at $x \sim 0.2$ in $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ is reasonably larger than that of $\text{Na}_{1-x}\text{CoO}_2$ occurring at $x < 0.1$ [3], since the vacancy potential of Sr^{2+} is stronger than that of Na^+ , although single crystal data will be helpful for further investigations [49]. Another point to be noted is, when a nonmetallic transport is realized by randomness in a spin-orbitally degenerate system such as in $\text{Fe}_3\text{O}_{4-x}\text{F}_x$ [50], a hump feature occurs at $T \sim 100\text{K}$ in a Q - T curve [49, 50, 51]. This feature is very similar to the enhanced Q at $\sim 100\text{K}$ in metallic $\text{Na}_{1-x}\text{CoO}_2$ at low x [3], which is considered to be on the verge of the metal-nonmetal transition. Further studies are necessary to clarify the relationship between the randomness and the transport properties in the rhodates and the cobaltates particularly at low x .

In summary, we have performed resonant PES and XAS on $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ and find that the holes have strong O 2p character. The VBS, which commonly occurs in the TE cobaltates, is proven from resonant PES at the O 1s edge to be a fingerprint of the O 2p holes in the

initial state. The results indicate a non-rigid-band evolution of the electronic structure with doping due to the d - p rehybridization affected by the cation vacancy potentials [27, 28, 29, 30], resulting in an inhomogeneous charge texture that may affect the transport properties at low

x .

Y.I. acknowledge A. Mizutani, K. Sugiura, H. Ohta, and I. Matsuda for informative discussion and T. Mizokawa for critical reading of the manuscript.

-
- [1] G. Mahan, B. Sales, and J. Sharp, *Physics Today* **42** (1997).
 - [2] I. Terasaki, Y. Sasago, and K. Uchinokura, *Phys. Rev. B* **56**, R12685 (1997).
 - [3] M. Lee *et al.*, *Nat. Mater.* **5**, 537 (2006).
 - [4] M. L. Foo, Y. Wang, S. Watauchi, H. W. Zandbergen, T. He, R. J. Cava, and N. P. Ong, *Phys. Rev. Lett.* **92**, 247001 (2004).
 - [5] K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian, and T. Sasaki, *Nature* **422**, 53 (2003).
 - [6] J. Sugiyama, J. H. Brewer, E. J. Ansaldo, B. Hitti, M. Mikami, Y. Mori, and T. Sasaki, *Phys. Rev. B* **69**, 214423 (2004).
 - [7] S. P. Bayrakci *et al.*, *Phys. Rev. Lett.* **94**, 157205 (2005).
 - [8] D. J. Singh, *Phys. Rev. B* **61**, 13397 (2000).
 - [9] T. Takeuchi *et al.*, *Phys. Rev. B* **69**, 125410 (2004).
 - [10] H. J. Xiang and D. J. Singh, *Phys. Rev. B* **76**, 195111 (2007).
 - [11] K. Kuroki and R. Arita, *J. Phys. Soc. Jpn.* **76**, 083707 (2007).
 - [12] W. Koshibae, K. Tsutsui, and S. Maekawa, *Phys. Rev. B* **62**, 6869 (2000).
 - [13] Y. Wang, N. S. Rogado, R. J. Cava, and N. P. Ong, *Nature* **423**, 425 (2003).
 - [14] O. I. Motrunich and P. A. Lee, *Phys. Rev. B* **69**, 214516 (2004).
 - [15] J. O. Haerter, M. R. Peterson, and B. S. Shastry, *Phys. Rev. Lett.* **97**, 226402 (2006).
 - [16] P. Limelette, S. Hebert, V. Hardy, R. Fresard, C. Simon, and A. Maignan, *Phys. Rev. Lett.* **97**, 046601 (2006).
 - [17] Y. Ishida, H. Ohta, A. Fujimori, and H. Hosono, *J. Phys. Soc. Jpn.* **76**, 103709 (2007).
 - [18] M. Roger *et al.*, *Nature* **445**, 631 (2007).
 - [19] F. C. Chou *et al.*, *Phys. Rev. Lett.* **101**, 127404 (2008).
 - [20] C. A. Marianetti and G. Kotliar, *Phys. Rev. Lett.* **98**, 176405 (2007).
 - [21] M. Gao, S. Zhou, and Z. Wang, *Phys. Rev. B* **76**, 180402(R) (2007).
 - [22] M.-H. Julien *et al.*, *Phys. Rev. Lett.* **100**, 096405 (2008).
 - [23] M. Z. Hasan *et al.*, *Phys. Rev. Lett.* **92**, 246402 (2004).
 - [24] J. van Elp, J. L. Wieland, H. Eskes, P. Kuiper, and G. A. Sawatzky, *Phys. Rev. B* **44**, 6090 (1991).
 - [25] T. Mizokawa, L. H. Tjeng, P. G. Steeneken, N. B. Brookes, I. Tsukada, T. Yamamoto, and K. Uchinokura, *Phys. Rev. B* **64**, 115104 (2001).
 - [26] Y. Okamoto, M. Nohara, F. Sakai, and H. Takagi, *J. Phys. Soc. Jpn.* **75**, 023704 (2006).
 - [27] C. Wolverton and A. Zunger, *Phys. Rev. Lett.* **81**, 606 (1998).
 - [28] C. A. Marianetti, G. Kotliar, and G. Ceder, *Nat. Mater.* **3**, 627 (2004).
 - [29] C. A. Marianetti, G. Kotliar, and G. Ceder, *Phys. Rev. Lett.* **92**, 196405 (2004).
 - [30] H. Raebiger, S. Lany, and A. Zunger, *Nature* **453**, 763 (2008).
 - [31] H. Ohashi *et al.*, *AIP Conf. Proc.* **879**, 523 (2007).
 - [32] G. B. Wilson-Short, D. J. Singh, M. Fornari, and M. Suenwattana, *Phys. Rev. B* **75**, 035121 (2007).
 - [33] C. Guillot *et al.*, *Phys. Rev. Lett.* **39**, 1632 (1977).
 - [34] W. B. Wu, D. J. Huang, J. Okamoto, A. Tanaka, H.-J. Lin, F. C. Chou, A. Fujimori, and C. T. Chen, *Phys. Rev. Lett.* **94**, 146402 (2005).
 - [35] T. Kroll, A. A. Aligia, and G. A. Sawatzky, *Phys. Rev. B* **74**, 115124 (2006).
 - [36] Since the charge densities of $\text{Li}_{1-x}\text{CoO}_2$ [27, 28] and $\text{Na}_{1-x}\text{CoO}_2$ [29] are strongly affected by the cation vacancies, it is not *a priori* to adopt the symmetry of a CoO_6 octahedra [34, 35] to understand the electronic structures of the cobaltates.
 - [37] L. A. Montoro, M. Abbate, and J. M. Rosolen, *Electrochem. Solid-State Lett.* **3**, 410 (2000).
 - [38] V. R. Galakhov *et al.*, *Phys. Rev. B* **74**, 045120 (2006).
 - [39] T. Kroll, M. Knupfer, J. Geck, C. Hess, T. Schwieger, G. Krabbes, C. Sekar, and D. R. Batchelor, *Phys. Rev. B* **74**, 115123 (2006).
 - [40] Even though LDA DOS cannot reproduce VBS since LDA does not treat dynamical correlations in the electron removal state [52], charge densities, which are initial-state properties and are considered to be less affected by dynamical correlations, are nicely explained by LDAs.
 - [41] F. D. M. Haldane and P. W. Anderson, *Phys. Rev. B* **13**, 2553 (1976).
 - [42] F. L. Ning and T. Imai, *Phys. Rev. Lett.* **94**, 227004 (2005).
 - [43] K. Okada and A. Kotani, *J. Phys. Soc. Jpn.* **63**, 3176 (1994).
 - [44] M. Umeda, Y. Tezuka, S. Shin, and A. Yagishita, *Phys. Rev. B* **53**, 1783 (1996).
 - [45] Y. Ishida *et al.*, *Phys. Rev. Lett.* **100**, 056401 (2008).
 - [46] G. Wu, H. X. Yang, L. Zhao, X. G. Luo, T. Wu, G. Y. Wang, and X. H. Chen, *Phys. Rev. B* **76**, 024513 (2007).
 - [47] C. Umrigar, D. E. Ellis, D. Wang, H. Krakauer, and M. Posternak, *Phys. Rev. B* **26**, 4935 (1982).
 - [48] N. F. Mott, *Metal-Insulator Transitions*, 2nd edition (Taylor & Francis, 1990).
 - [49] K. Sugiura, H. Ohta, Y. Ishida, R. Huang, T. Saito, Y. Ikuhara, K. Nomura, H. Hosono, and K. Koumoto, *Appl. Phys. Express* **2**, 035503 (2009).
 - [50] H. Graener, M. Rosenberg, T. E. Whall, and M. R. B. Jones, *Philos. Mag. B* **40**, 389 (1979).
 - [51] I. P. Zvyagin, *The Hopping Thermopower in Hopping Transport in Solids*, edited by M. Pollak and B. Shklovskii, *Modern Problems in Condensed Matter Sciences Vol. 28* (North-Holland, Amsterdam, 1991).
 - [52] J. Kunes, V. I. Anisimov, S. L. Skornyakov, A. V. Lukoyanov, and D. Vollhardt, *Phys. Rev. Lett.* **99**, 156404 (2007).